

Laboratory Reference: CAN11W2723

ADHESION AGENT TEST REPORT

ATTENTION:

Ray Georgey

CLIENT: Otech Australia
 CLIENT REFERENCE: 0.7pph Otech AGGBIND-75[®] by volume at 15°C
 ADHESION AGENT: Otech AGGBIND-75[®] liquid adhesion agent
 ADHESION AGENT SOURCE: Supplied by Fulton Hogan Canterbury Bitumen Plant in May 2011
 AGGREGATE SOURCE: Sampled from Transfield Services – Puketona Road in September 2011
 TEST METHOD USED: WDSC B301-89T
 TESTED BY: Olimpia Zimcea & Rachel Smith on 8/11/2011

RESULTS:

| AGGREGATE SOURCE | AGENT QUANTITY (PPH BY VOLUME) | TEST RESULT | TEST CRITERION |
|-------------------------------------|-----------------------------------|----------------------------|----------------------|
| Transfield Services – Puketona Road | 0.7 | 89 Spec : 80 min | 1.25 Spec : 2 max |

Test performed using: Grade 3 chip of Puketona Road - Paihia origin
 Chip sieved between 13.2 & 9.5mm sieves and washed in deionised water
 180/200 Penetration Grade Bitumen
 Adhesion agent set up time was 2.5 hours
 Test temperature of 25°C

Report Issued By: Suzanne Lee on 9/11/2011

Report Checked By:


 Bitumen Laboratory Supervisor

Disclaimer: These test results apply to the samples as received by the Laboratory. No liability will be accepted by the Laboratory for any misrepresentation with respect to the sampling of material for testing and/or the use of these test results.

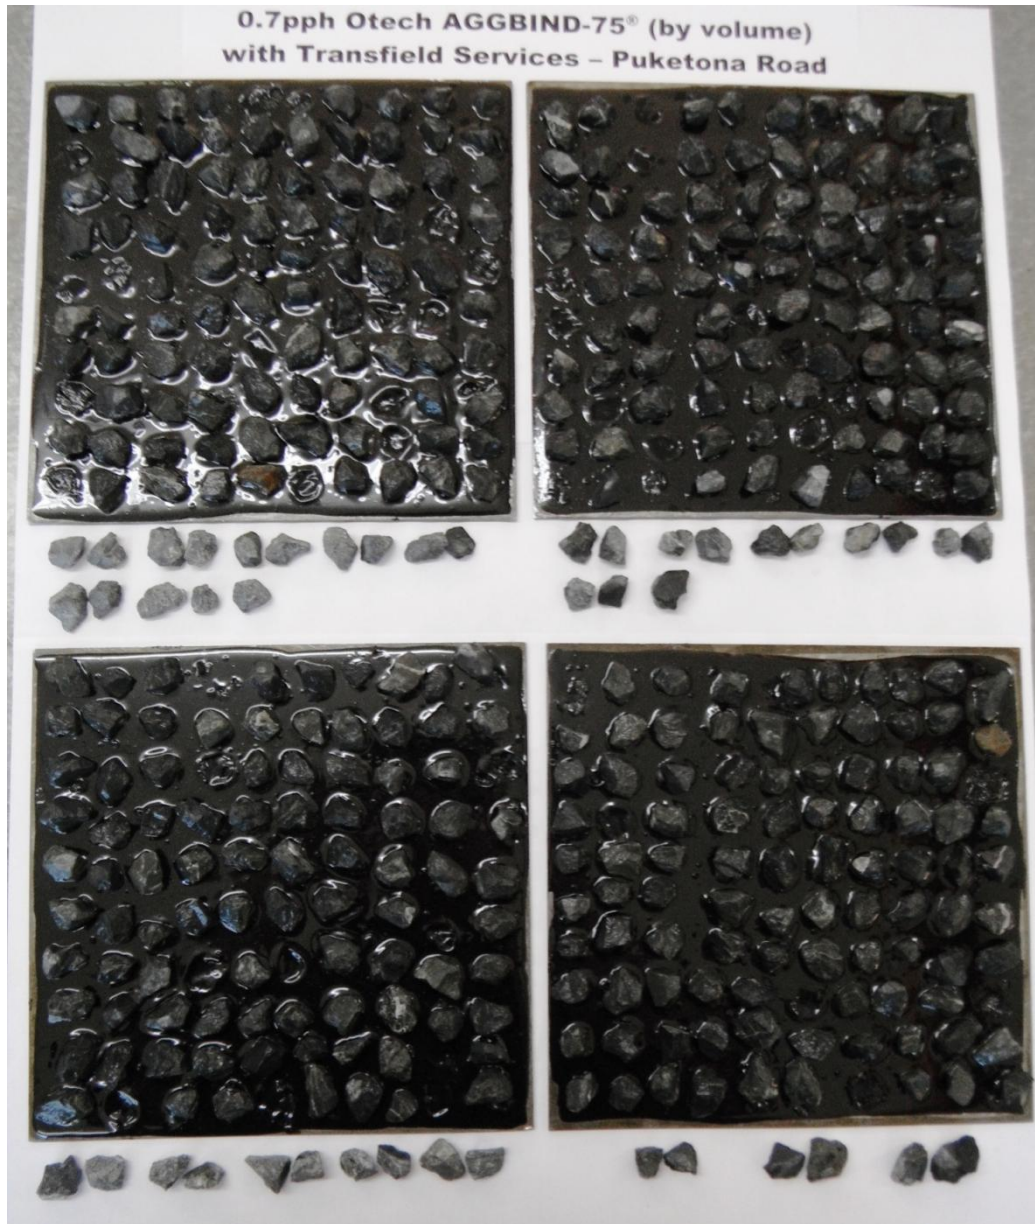


Figure 1. Photograph showing test plates with 180/200 bitumen and 0.7pph Otech AGGBIND-75® (by volume) after test was performed. Transfield Services – Puketona Rd grade 3 chip that was dislodged is arranged below the plates.